

Residual Stress in Plasma Sprayed Ceramic Turbine Tip and Gas Path Seal Specimens

R. C. Hendricks and G. McDonald

Lewis Research Center

Cleveland, Ohio

and

R. L. Mullen

Case Western Reserve University

Cleveland, Ohio

Prepared for the
Seventh Annual Conference on Ceramics and Advanced Materials
sponsored by the American Ceramic Society
Cocoa Beach, Florida, January 16-23, 1983



RESIDUAL STRESS IN PLASMA SPRAYED CERAMIC
TURBINE TIP AND GAS PATH SEAL SPECIMENS

R.C. Hendricks and G. McDonald
National Aeronautics and Space Administration
Lewis Research Center
Cleveland Ohio 44135

R.L. Mullen
Case Western Reserve University
Department of Civil Engineering
Cleveland Ohio 44106

ABSTRACT

The residual stresses in a ceramic sheet material used for turbine blade tip gas path seals, have been estimated. These stresses result from the plasma spraying process which leaves the surface of the sheet in tension. To determine the properties of plasma sprayed $ZrO_2-Y_2O_3$ sheet material, its load-deflection characteristics were measured. Estimates of the mechanical properties for sheet materials were found to differ from those reported for plasma sprayed bulk materials.

INTRODUCTION

Plasma spraying of ceramics on a suitably prepared metallic substrate is a widely used process for applying chemically, electrically or thermally insulative coatings. Such a plasma sprayed ceramic is of interest as part of a high temperature seal to increase the efficiency of operation of gas turbine engines. Since it is both nonoxidizing and refractory, refs. 1 and 2, plasma sprayed ceramics have also been extensively promoted as a means of increasing the life of highly stressed engine hot components by permitting operation at equilibrium gas temperature and thermodynamic efficiency but at lower component temperature, ref. 3-5.

However, the durability of the plasma sprayed ZrO_2 has not been generally adequate under the high temperature and heat transfer occurring in

gas turbine engines, ref. 6-8. The successful application of such ceramics requires a better understanding of the stresses generated during fabrication and at service conditions. This report describes the stresses generated due to deposition by the plasma spraying processes.

EXPERIMENTAL PROCEDURE

Materials and Coating Procedure

A 304-Stainless steel strip (0.15 x 1.9 x 12.7 cm) was coated with NiCrAlY bondcoat and ZrO_2 ceramic by first grit blasting with Al_2O_3 and plasma spraying on one flat surface in air with a 0.013 cm Ni18Cr12Al10.3Y bondcoat and then with ZrO_2 -8- or 12- wt. percent Y_2O_3 .

After spraying, the stainless steel and bondcoat were removed by dissolution in hydrochloric acid and the ZrO_2 - Y_2O_3 was washed in water and dried to leave a free form ceramic sheet.

Curvature and Deflection Measurements

The curvature of the 0.038 cm ZrO_2 - Y_2O_3 after removal from the metal substrate was measured under zero load by curve fitting. The load vs deflection of the ceramic strip was measured by clamping one end of the strip and loading the other end of the strip as a cantilever beam. Incremental loading was added to the end of the strip and deflection was measured using a grid background. The apparatus is shown schematically in figure 1. Table I shows the geometric and material properties of the ceramic sheet specimens tested.

RESULTS AND DISCUSSION

Experimental Results

A ZrO_2 -8 Y_2O_3 sheet stripped from its bondcoat and substrate is shown in figure 2. The sheet was loaded as a beam to determine the load/deflection characteristics (see table I and figure 1). The results are presented in

tables II and III and plotted in figures 3 and 4. A portion of the strain is non-elastic and non-recoverable, as the $\text{ZrO}_2\text{-Y}_2\text{O}_3$ sheet is unloaded, but after the initial loading to any given maximum load, subsequent loading and unloading is elastic up to that load as shown in figure 3. The deflection is linear (recoverable) up to a loading of 1.9 gm added load. Above an added load of 1.9 gm, a permanent offset is produced. We speculate that microcracking of the tensile surface occurs which produces a permanent set in the specimen. Even though an offset is produced the ceramic response is elastic up to each maximum load. Despite the offset, the elastic modulus is not changed significantly (as illustrated in figure 4). This can also be seen from the three distinct steps in the initial load-deflection data of specimen 7-2 (Table III). The added load required to produce sufficient set to remove all residual bending due to the stresses generated by plasma spraying process, see figure 2, is 3.5 gm added load.

The radius of curvature of stripped sheets before loading (figure 2) averages 29.7 cm. The curvature bows away from the metal substrate. Further, the curvatures along the width and length are equal. This is characteristic of a uniformly stressed plate or sheet. For $\text{ZrO}_2\text{-12Y}_2\text{O}_3$ plasma sprayed at conditions similar to those described above, the curvatures of the stripped $\text{ZrO}_2\text{-12Y}_2\text{O}_3$ free form ceramics were the same.

Analysis

The stainless steel, after plasma spraying with NiCrAlY and 0.038 cm of $\text{ZrO}_2\text{-Y}_2\text{O}_3$, is straight and flat. After removal of the stainless steel and bond coat, the $\text{ZrO}_2\text{-Y}_2\text{O}_3$ curves to relieve the residual stresses in the $\text{ZrO}_2\text{-Y}_2\text{O}_3$ ceramic. These residuals are due to the fabrication process of plasma spraying onto the metal substrate. The residual strain on the outside surface of the ceramic due to plasma spraying is

$$\epsilon = \frac{\Delta l}{l} = \frac{t}{R} = \frac{.038}{29.7} = 1.25 \times 10^{-3} \frac{\text{cm}}{\text{cm}}$$

The strains associated with mechanical deformation of the coated substrate are discussed in the Appendix.

The tensile stress in the $\text{ZrO}_2\text{-Y}_2\text{O}_3$ is due to the rapid quench of the plasma sprayed particle as it impacts the solid. The side of the impacted particle facing the atmosphere cools more slowly by convection and radiation. The plasma spraying is a non equilibrium process in that a particle heated to high temperature in the plasma is impacted onto a much colder substrate where it is rapidly solidified. The side of the impacted particle away from the substrate can flow plastically as it cools to relieve stress until it reaches approximately 1000 C, (ref. 9). Below 1000 C, plastic flow is too slow to relieve stress and the thermal contraction from 1000 C to ambient appears as a residual tensile stress.

$$\begin{aligned} \text{Strain due to thermal contraction} &= \epsilon = \alpha \Delta T = 8.3 \times 10^{-6} \times 1 \times 10^3 \\ &= 8.3 \times 10^{-3} \text{ cm/cm.} \end{aligned}$$

These residual stresses are relieved by straining the free-form ceramic sheet, and to account for the bending of the ceramic sheet. The exact temperature for the end of plastic flow of the $\text{ZrO}_2\text{-Y}_2\text{O}_3$ is uncertain and it may be that some plastic flow occurs to some temperature somewhat below 1000 C, ref. 9.

From the beam flexure measurements, the elastic modulus ranges from 0.5 to 1.0×10^6 psi with a limiting bending stress of 1800 psi as determined by extrapolating the load and deflection data of table III. The elastic modulus for the plasma sprayed sheet specimens is a factor of ten less than those measured in ref. 4 for plasma sprayed coatings while the bending stresses are about half those given in ref. 4. There is little doubt that some

microcracking does occur, however the sheet specimens not only remain intact when stripped from the substrate, but are sufficiently flexible to function as cantilever beams with distinct characteristics.

SUMMARY

The residual stresses in a ceramic sheet material due to plasma spraying have been calculated from the measured bending which occurs when the sheet is removed from the metal substrate. The surface of the sheet after plasma spraying on the substrate is in tension. The tension results from the rapid cooling and solidification of the hot and plastic plasma sprayed ceramic particle as it impacts the substrate. The residual stress resulting from the plasma spraying has also been measured directly from the force required to remove the bending.

The elastic modulus of these plasma sprayed specimens is a factor of ten less than that reported for similar plasma sprayed ceramics.

SYMBOLS

$\langle Co \rangle$	average width of cracked material
E	elastic modulus
l	length
N	number of cracks
R	radius of curvature
t	thickness
w	width
α	thermal expansion
σ_t	stress
Δ	increment
ϵ	strain

APPENDIX

Mechanical Deformation of Coated Substrates

Mechanical deformation cited in reference 10, gives a crack spacing of

$$\omega = 0.02 + 73t^2$$

and measurements of the curvature of the tensile cracked specimens, figure 5, gives,

$$R = 50t$$

or the number of 'visible' surface cracks (e.g., figure 6) becomes

$$N = \frac{\pi(R+t)}{\omega} = \frac{102\pi}{0.02 + 73t^2}$$

For N uniformly spaced cracks, the largest the average spacing can be is when

$$\Delta l = 2\pi t = N\langle Co \rangle$$

Solving, for a 0.020" thick coating,

$$\langle Co \rangle = \frac{\omega}{1 + \frac{R}{t}} = .001 \text{ in.}$$

From the photograph, figure 6, spacing between cracks appear for the unaided eye to 0.004" to those which can only be seen at 50X or higher. For $\sigma_t = 10^4$ psi, $E = 5 \times 10^6$ psi and $t = 0.020$ in, the calculated $\langle Co \rangle$ becomes

$$\epsilon = \frac{\Delta l}{l} = \frac{N\langle Co \rangle}{2\pi r} = \frac{\sigma_t}{E}$$
$$\langle Co \rangle = \frac{\omega \alpha t}{E(1 + \frac{t}{R})} = 10^{-4} \text{ in.}$$

or one order of magnitude less than the maximum value of $\langle Co \rangle$. Furthermore, if the parameters, $\alpha_t = 10^3$ psi and $E = 0.5 \times 10^6$ psi, are characteristic of sheet specimens, then $\langle Co \rangle$ is the same.

The coating losses at the edges of the bar are due to double curvature which places the edges in compression and often appear to be sufficient to delaminate the ceramic.

REFERENCES

1. Kingery, W.D. ; Bower, H.K.; Uhlmann, D.R.: Introduction to Ceramics. John Wiley and Sons, NY.
2. Shaud, E.B.: Glass Engineering Handbook, 2ed. 1958, McGraw-Hill.
3. Sinko, G.S.; Cassenti, Brice. N. and Brickley, Ann M.: JT9D Thermal Barrier Coating Analysis Informal Report. Pratt & Whitney Aircraft Group, PWA-55155-135, Contract NAS3-20630, Sept. 1980.
4. Andersson, C.A.; Bratton, R.J.; Lau, S.K.; Lee, S.Y.; Allen, J.; Munsen, K.E.; Rieke, K.L.; Advanced ceramic coating development for industrial/utility gas turbines. Westinghouse 5th Quarterly progress report to NASA DEN 3-110, Jan. 1981.
5. Leibert, Curt H. and Stepka, Francis S.: Ceramic Thermal-Barrier Coatings for Cooled Turbines, J. Aircraft Vol 14 no 5, May 1977, pp 487,493.
6. McDonald, G. and Hendricks, R.C.: Effect of Thermal Cycling on ZrO₂-Y₂O₃ Thermal Barrier Coatings, NASA TMX-81480 (1980). See also, Thin Solid Films 73 (1980) 491-496.
7. R. C. Hendricks and G. McDonald, " Assessment of Variations in Thermal Cycle Life Data of Thermal Barrier Coated Rods," NASA TM 81743, (1981). See also, Thin Solid Films 74 (1981)
8. Hendricks, R.C.; McDonald, G. and Poolos, N.J: Prolonging thermal barrier coated specimen life by effective thermal management. NASA TM 81742, (1981).
9. Hendricks R.C., McDonald G., and Mullen, R.L.: Annealing of Creep of Plasma Sprayed Ceramics. Paper 54-C-83C, 7th Annual Conf. on Composites and Advanced Ceramic Materials, Am. Ceramic Soc., Cocoa Beach FL, Jan 16-19, 1983.

10. Mullen, R.L., McDonald, G., Hendricks, R.C. and Hofle, M.L.: Correlation of Compressive Stress with Spalling of Ceramic Coatings. 53-C-83C, 7th Annual Conf. on Composites and Advanced Ceramic Materials, Am. Ceramic Soc., Cocoa Beach FL, Jan 16-19, 1983.

Table I. Geometric and Material Properties of Ceramic Sheet Specimens

Sample	Material	Heating	Weight gmf	Density gm/cc	Width mm inch	Avg. Thickness mm inch	Length mm inch	Loaded length mm inch	clamped length mm inch
2a-1	ZrO ₂ -8Y ₂ O ₃	As sprayed	3.7773	3.94	19 .75	.41 .016	123.8 4.875	76.2 3.0	41.4 1.63
7-1	ZrO ₂ -8Y ₂ O ₃	1200 C (2200 F) 24 hr	2.7862	3.189	19 .75	.46 .018	100.3 3.95	85.1 3.35	10.2 .4
7-2	ZrO ₂ -12Y ₂ O ₃	1200 C (2200 F) 24 hr	3.6988	3.605	19 .75	.53 .021	101. 3.975	84.5 3.33	10.2 .4

Table II. Load Deflection Values for Ceramic Sheet Specimens

Sample	Ref. grid value (cm)	Load (gmf)	0	0.907	1.907	2.907	3.907	4.907
2a-1	load application							
	increasing load		1.8	2.4	2.8	3.2	3.8	4.3
	decreasing load		2.8	3.2	3.4	3.9	4.1	4.3
	3-cycle Avg.		2.8	3.18	3.43	3.8	4.09	4.37
7-1	increasing load		0	.5	.9	1.4	1.9	2.6
	decreasing load		.5	1.0	1.4	2.0	2.4	2.6
	4-cycle Avg.		.5	1.0	1.37	1.84	2.27	2.65

	Ref. grid value (cm)	Load (gmf)	0	0.9	1.9	2.9	3.9	4.9	5.9	7.9	8.9	9.9	10.9	12.9
7-2	load application													
	increasing load			-.3	-.2	-.1	0.	.1	.2	.6	.7	.8	1.1	1.3
	decreasing load			-.2	-.1	.1	.3		.6	.8	.8		1.2	1.4
	3-cycle Avg.			-.2		.1	.24		.56	.76	.84		1.2	1.4

Table III. Load Deflection Values with Inelastic Behavior for Ceramic Sheet Specimens

Specimen	Ref. grid value (cm)	Load (gmf)	0	Self	0.908	1.908	2.908	3.908	4.908	5.908
	load application									
2a - 2		2.3	2.7							
same as	increasing load	2.3	2.7	3.1	3.4					
2a-1	decreasing load			3.1	3.4					
	increasing load				3.4	3.8				
	decreasing load			3.2	3.5	3.8				
	increasing load			3.4	3.6	4.0	4.2			
	decreasing load					3.9	4.2	4.6		
	increasing load			3.5	3.7	4.1	4.3	4.6		
	decreasing load			3.7	4.0	4.4	4.7	5.0	5.3	
	increasing load				3.9	4.2	4.5	5.0	5.3	
	decreasing load			3.7	4.0	4.5	4.7	5.0	5.3	

Horizontal = 3.9 cm

Self-load defined as zero = 2.3 cm

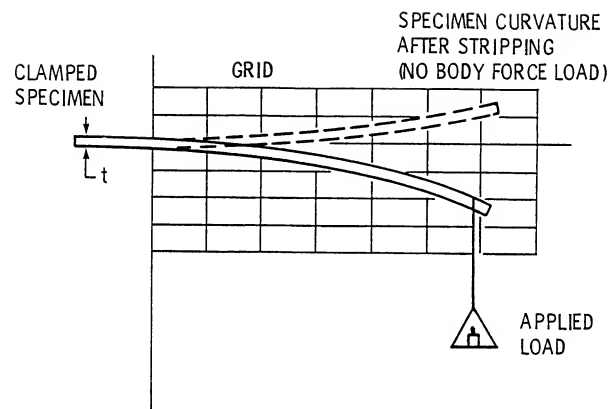


Figure 1. - Schematic of load-deflection apparatus.

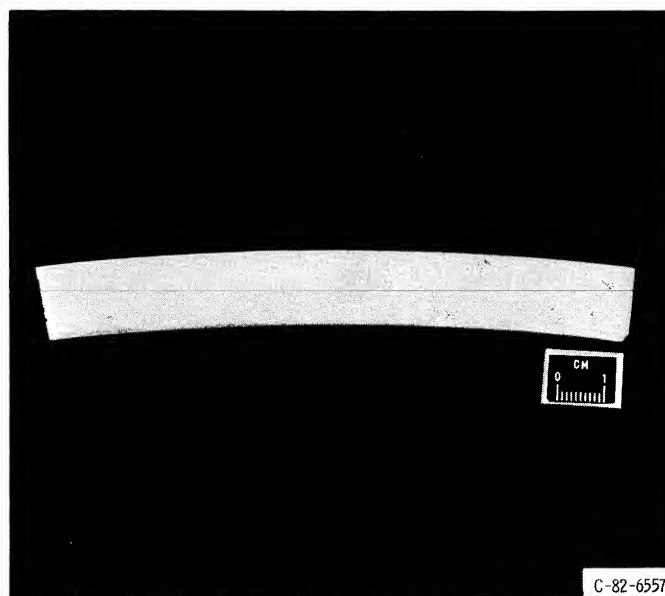


Figure 2. - Photograph of plasma sprayed sheet stripped from it's substrate.

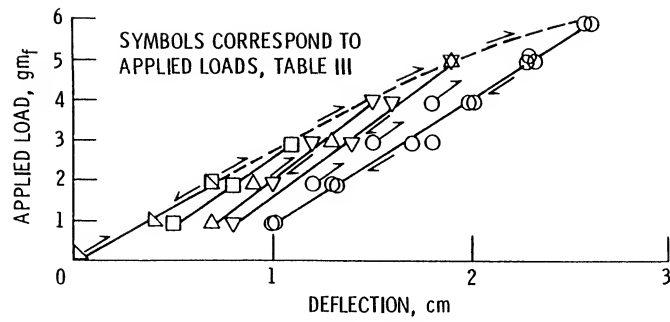


Figure 3. - Elastic and inelastic load-deflection characteristics of plasma sprayed sheet specimens.

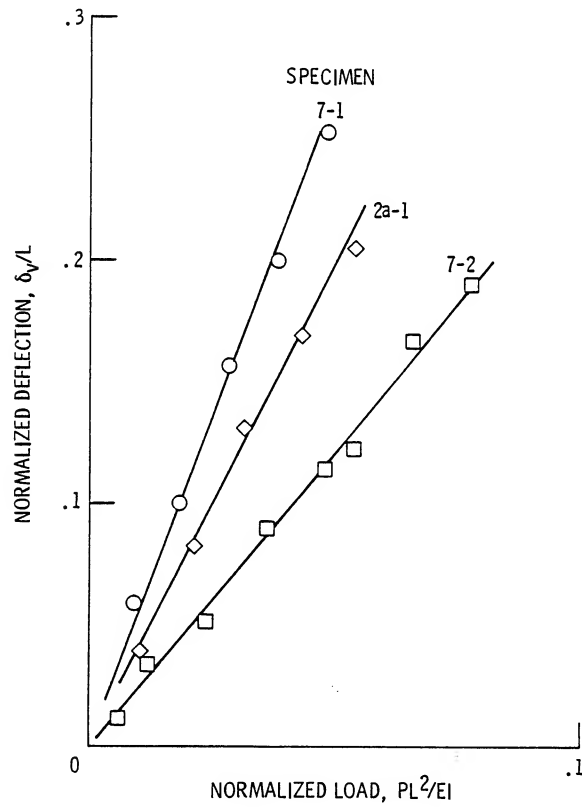


Figure 4. - Normalized load-deflection characteristics for plasma sprayed sheet specimens.

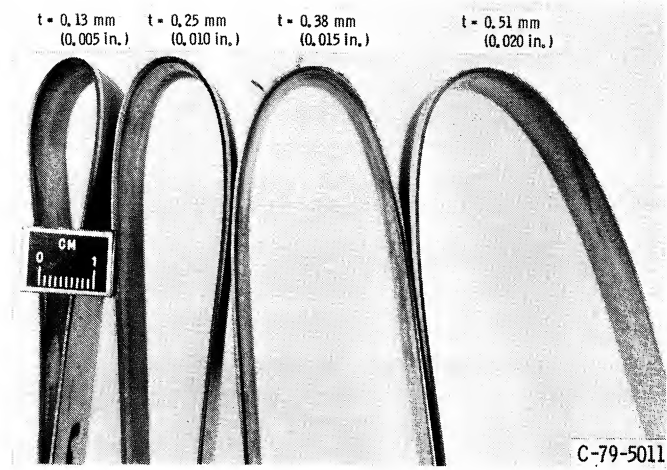


Figure 5. - Curvature due to mechanical cracking of plasma sprayed sheet attached to it's substrate.

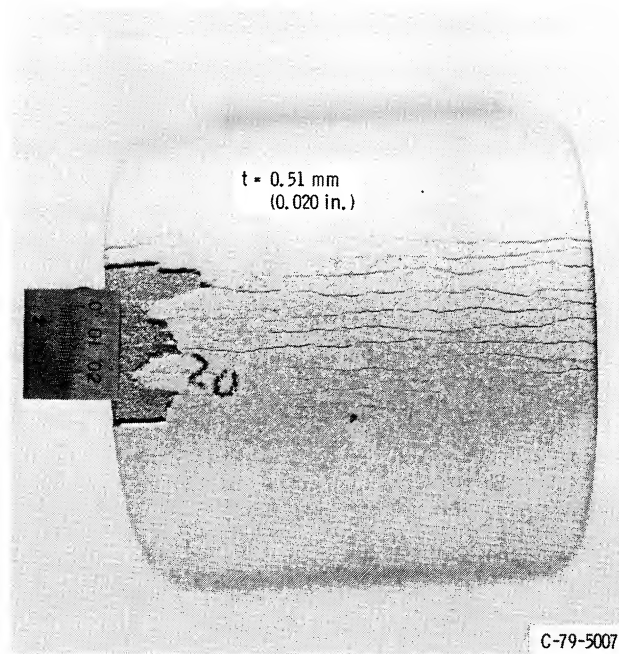


Figure 6. - Mechanical crack spacing of plasma sprayed sheet attached to it's substrate.

1. Report No. NASA TM-83418		2. Government Accession No.		3. Recipient's Catalog No.	
4. Title and Subtitle RESIDUAL STRESS IN PLASMA SPRAYED CERAMIC TURBINE TIP AND GAS PATH SEAL SPECIMENS				5. Report Date	
				6. Performing Organization Code 505-33-52	
7. Author(s) R. C. Hendricks, G. McDonald, and R. L. Mullen				8. Performing Organization Report No. E-1706	
				10. Work Unit No.	
9. Performing Organization Name and Address National Aeronautics and Space Administration Lewis Research Center Cleveland, Ohio 44135				11. Contract or Grant No.	
				13. Type of Report and Period Covered Technical Memorandum	
12. Sponsoring Agency Name and Address National Aeronautics and Space Administration Washington, D.C. 20546				14. Sponsoring Agency Code	
15. Supplementary Notes R. C. Hendricks and G. McDonald, NASA Lewis Research Center; R. L. Mullen, Case Western Reserve University, Department of Civil Engineering; Cleveland, Ohio 44106. Prepared for the Seventh Annual Conference on Ceramics and Advanced Materials sponsored by the American Ceramic Society, Cocoa Beach, Florida, January 16-23, 1983.					
16. Abstract The residual stresses in a ceramic sheet material used for turbine blade tip gas path seals, have been estimated. These stresses result from the plasma spraying process which leaves the surface of the sheet in tension. To determine the properties of plasma sprayed $ZrO_2-Y_2O_3$ sheet material, its load-deflection characteristics were measured. Estimates of the mechanical properties for sheet materials were found to differ from those reported for plasma sprayed bulk materials.					
17. Key Words (Suggested by Author(s)) Plasma Spray Ceramics Seals Residual Stress				18. Distribution Statement Unclassified - unlimited STAR Category 34	
19. Security Classif. (of this report) Unclassified		20. Security Classif. (of this page) Unclassified		21. No. of pages	
				22. Price*	